

## Adsorption Study of the Lysozyme from aqueous solution onto Hydroxyapatite Nanopowders

O. Moradi<sup>1,\*</sup> and K. Zare<sup>2,3</sup>

<sup>1</sup> Department of Chemistry, Shaher-e- Qods- Branch, Islamic Azad University, Shaher-e- Qods, Iran

<sup>2</sup> Department of Chemistry, Shahid Beheshti University, Evin, Tehran, Iran

<sup>3</sup> Department of Chemistry, Science and Research Branch, Islamic Azad University, Tehran, Iran

Received December 2010; Accepted February 2011

### ABSTRACT

In this study, a series of laboratory tests were conducted to investigate the efficiency of hydroxyapatite (HAP) nanopowders towards adsorption of lysozyme from aqueous solution. In the present research, HAP nanopowders synthesized from egg-shell characterized using SEM and FT-IR. The adsorption of lysozyme was 1 mg/mL using 0.1 g adsorbent in 100 mL of lysozyme solution. Adsorption data were fitted to a linearly Langmuir isotherm. Thermodynamics parameters were also calculated to study the effect of temperature on adsorption process. An adsorption kinetic study revealed that the adsorption process followed first order kinetics.

**Keywords:** Hydroxyapatite; Nanopowders; Lysozyme; Adsorption; Thermodynamic parameters

### INTRODUCTION

Calcium hydroxyapatite [ $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$ ] is in the space group P63/m; its unit cell parameters are  $a = b = 0.943$  nm and  $c = 0.688$  nm, and it possesses two different binding sites (C and P sites) on the particle surface. Thus, it contains a multiple site binding character for proteins [1–3]. The crystal structure of HAP is depicted in Fig. 1. After dispersing HAP particles in the aqueous media, calcium atoms (C sites) are exposed on the Hap surface by dissolution of  $\text{OH}^-$  ions at the particle surface.

Hence, HAP is widely applied for to separating various proteins in a high-performance liquid chromatograph (HPLC) system [4, 5]. In the past decade, some authors have conducted fundamental studies of the adsorptions of bovine serum albumin (BSA: isoelectric point ( $\text{P}_i$ ) = 4.7, molecular mass = 67200 Da), lysozyme ( $\text{P}_i$  = 11.1, molecular mass = 14600 Da), lysozyme onto various kinds of synthetic HAP particles [6–12]. These studies clarified that the saturated amount of adsorbed BSA depends on the molar ratio of Ca to phosphate (Ca/P) of

the materials used. The adsorption of BSA is increased with an increase in the Ca/P ratio, due to the electrostatic attractive forces between negatively charged BSA and the less negatively charged HAP having high Ca/P ratios at pH 6. On the contrary, the saturated amounts of adsorbed lysozyme on HAP particles is decreased with an increase in the Ca/P ratio, but no remarkable relationship with the Ca/P ratio was detected for the neutral proteins [11, 12]. Other groups have also disclosed that the adsorption of BSA onto HAP is governed by  $\text{Ca}^{2+}$  ions complexing to BSA molecules (binding effect) together with the operation of C sites [13]. However, this binding effect of  $\text{Ca}^{2+}$  ions is minor because the fraction of dissolution of surface Ca ions of HAP is low (1.2–3.2%) in a neutral aqueous solution. Furthermore, since the number of functional groups is small, the binding effect of the counter ions was only slightly detected on the adsorption of lysozyme,

\*Corresponding author: moradi.omid@yahoo.com

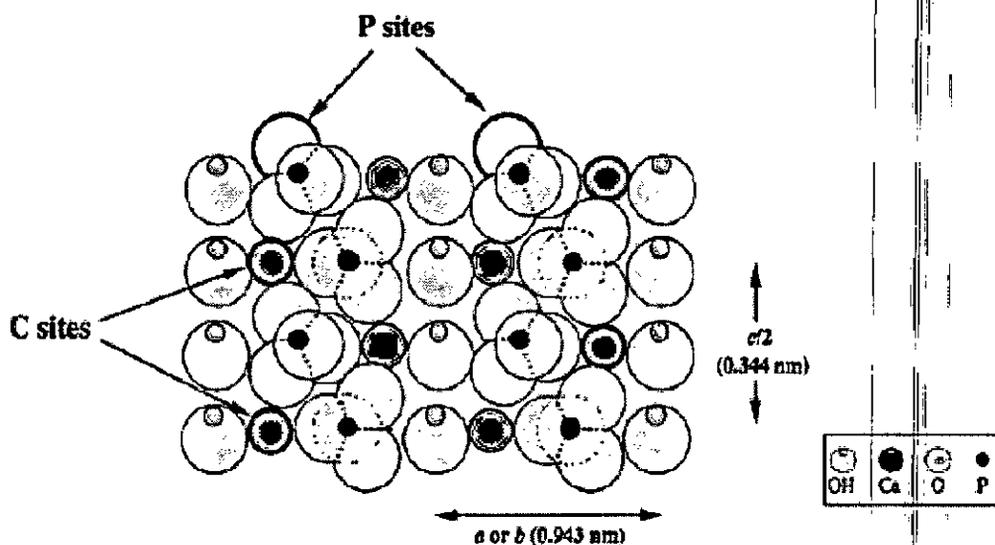


Fig. 1. Crystal structure of HAP from perpendicular to c-axis.

even though the systems could dissolve divalent and trivalent ions. Some authors investigated adsorption behavior of proteins onto HAP particles using a flow microcalorimeter. It has been found that the heat of adsorption of all proteins exhibits endothermic heat [14], i.e., the adsorption enthalpies ( $\Delta H_{ads}$ ) exhibited positive values. The  $\Delta H_{ads}$  values of all the proteins were decreased with an increase in the improvement of HAP crystallinity whereas desorption enthalpies ( $\Delta H_{des}$ ) were increased. This opposite results on  $\Delta H_{ads}$  and  $\Delta H_{des}$  revealed that HAP possesses a high adsorption affinity to proteins [14].

HAP nanopowders possess high biocompatibility and adsorption properties. They have been widely used as carriers for drugs and genes, adsorbents for chromatography to separate proteins, and removal of heavy metal ions to recover the contaminated soils, wastewater and fly ashes, etc. [15-21].

The objective of this study HAP was to characterize the nanopowders obtained from egg shell using SEM and FT-IR. As well as investigating the potential candidate of HAP nanopowders as a new biocompatible adsorbent for the adsorption of lysozyme from aqueous solution. The effects of contact time, initial lysozyme concentration, pH, temperature on the lysozyme adsorption, kinetic, equilibrium and thermodynamic parameters at various temperatures and concentration were investigated.


## MATERIALS AND METHODS

### Reagents and chemicals


Different chemicals used in the present study were of analytical grade and obtained from Merck. 10 mg/mL stock lysozyme solution was prepared by dissolving 10 mg of lysozyme (From Roche Biomolecular Company, Germany) in 25 mL freshly deionized water. The required concentration of lysozyme solution was obtained by serial dilution of 10 mg/mL lysozyme solution.

### Sample preparation

HAP samples were prepared from egg shells. The shells were first washed and dried. The pretreated (washed and dried) egg shell wastes were ground and sieved to powder (mesh size 30). Then, the egg shells were added to aqueous (1:1)  $H_3PO_4$ , kept at 303-313 K for 2-3 h, under pH:1-3. The following reaction took place:



Insoluble matter was separated and removed by filtration. Subsequently,  $Ca(OH)_2$  was added to the solution and was kept at 323-333 K for 24 h, The pH were adjusted 5-9 by 0.1 M HCl or NaOH. The following reaction represents the type of process that took place:



At last, the suspension was dried and ground to powder (mesh size 30) to get the sample.

### FT-IR studies

Study FT-IR of the sample was obtained using Perkin Elmer FT-IR spectrophotometer SPECTRUMRX-I. FT-IR spectrum of the sample was obtained by KBr pellet method. The ratio of the sample to KBr was 1:50.

### Scanning Electron Microscopy

Scanning electron micrograph of the sample was obtained by JEOL JSM - 6480 LV scanning electron microscope. The sample was coated with platinum for 30 s at current of 50 mA before the SEM micrograph was obtained.

### Batch experiments

The lysozyme adsorption experiments from its aqueous solution by HAP were carried out using standard 1, 2, 3 and 4 mg/mL lysozyme solution. The adsorption experiments were carried out in 250 mL glass conical flask provided with stopper, by adding 0.1 g of HAP in 100 mL of synthetic lysozyme solution. Stoppers were used to avoid change in concentration due to evaporation. All the experiments were carried out at ambient temperature ( $25 \pm 1^\circ\text{C}$ ). After continuous stirring over magnetic stirrer at about 400 rpm for a pre determined time interval, lysozyme concentration was determined by UV-Vis spectrometer ( $\lambda_{\text{max}}=280 \text{ nm}$ ). One standards were prepared bracket, the expected sample range and which differing concentration by a factor often. Measurements were done by taking 10 mL of standard and sample into separate 50 mL beaker and 25 mL of lysozyme interference suppressor. All the sample and standards were maintained at same temperature to avoid interference due to difference in temperature.

## RESULT AND DISCUSSION

### Characterization of hydroxyapatite

In Fig. 2 shows the FT-IR spectra of HAP prepared from egg shells. The spectra record dill defined and low intensity absorption bands of P-O due to  $\text{PO}_4^{3-}$  groups in the  $1052 \text{ cm}^{-1}$  region, which are characteristic of the HAP, as well as of the H-O bands of adsorbed water [22]. A well distinguished peak at  $607 \text{ cm}^{-1}$  indicates the O-H vibration alamode. Band so shoulders at  $3467 \text{ cm}^{-1}$  is due O-H stretching of water of crystallization. The band at  $2923 \text{ cm}^{-1}$  is apparently due to  $\text{CO}_2$  background of the measurement system [23].

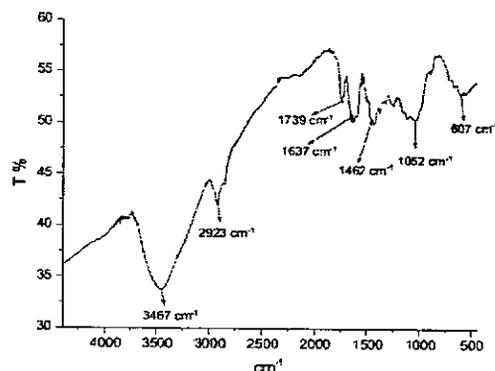


Fig. 2. FT-IR pattern of HAP.

The SEM micrograph of the sample obtained is shown in Fig. 3. Clusters of HAP particles have a homogenous size. The average size of the clusters was 300 nm.

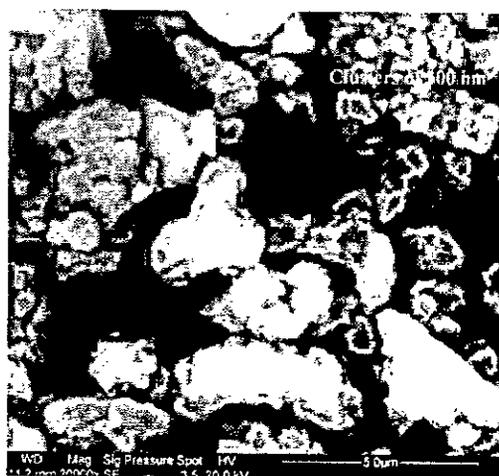


Fig. 3. SEM micrographs of HAP (Magnification - 20,000 X, 20 kV).

### Effect of pH on removal of lysozyme

pH of the aqueous solution is one of the main variable parameters in the adsorption process. The pH may affect the ionization degree of the sorbet and the surface property of the adsorbent [24]. Several different pH tests were carried out and the results are shown in Fig. 4. The percentage removal of lysozyme by HAP increased from 67% to 83% for increase in pH 5 to 9, for initial lysozyme concentration of 1 mg/mL. It is evident from the above data that there was increase in percent age removal for increase in pH from 5 to 9 but for further increase in pH beyond 7, there wasn't any increase in removal. It may due to the fact hat HAP is not stable under acidic condition and hence exhibited poor removal efficiency. And the percent age removal stood almost constant for pH 8-9. According to the results the pH does not affect the

percent agonist rate removed for pH 7 and above. However in the pH below 7 it has significant effect. There fore care must betake with acidic solutions.

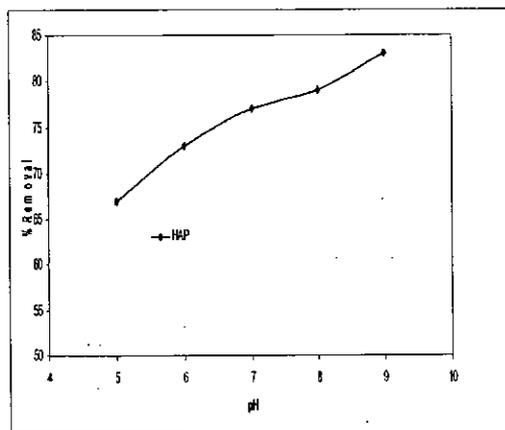


Fig. 4. pH versus percentage removal of lysozyme onto HAP.

**Effect of contact time and adsorption kinetics**

Adsorption of lysozyme at different contact time was studied for initial lysozyme concentration of 1, 2, 3 and 4 mg/mL keeping all other parameters constant. The result is presented in Fig. 5. The percentage removal was found to increase from 38% to 77%, 42% to 79%, 45% to 81% and 49% to 85% for a contact time of 5 min to 60 min and initial lysozyme concentration of 1, 2, 3 and 4 mg/mL, respectively. It is clear from the figure that about 50% removal took place within first 5 min and equilibrium was established after 60 min. The change in the rate of removal might be due to the fact that initially all adsorbents site contained replaceable hydroxide ion and resolute concentration gradient was also high.

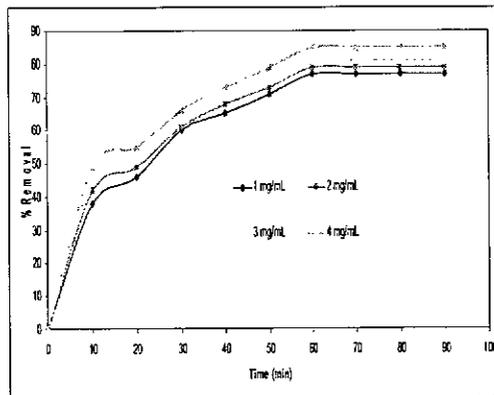


Fig. 5. Time versus percentage removal of lysozyme onto HAP with initial concentration of 1 mg/mL.

Later, the lysozyme up take rate by adsorbent was decreased significantly, due to the decrease in

number of replaceable hydroxide ions in adsorption sites as well as decrease in lysozyme concentration. Decreased removal rate, particularly, toward the end of experiments, indicates the possible monolayer formation of lysozyme ion on the outer surface. The rate constant  $K_{ad}$  for adsorption of lysozyme was studied by Lagergren rate equation for initial lysozyme concentration of 1, 2, 3 and 4 mg/mL [25-26]:

$$\ln(q_e - q_t) = \ln q_e - K_1 t \quad (1)$$


Also a linear form of pseudo-second order model (Eq. (2)), Ho and MaKay's pseudo-second order model [27], for the adsorption of lysozyme onto HAP was illustrated in Table 1.

$$\frac{t}{q_t} = \frac{1}{kq_e^2} + \frac{1}{q_e} t \quad (2)$$

where  $q_e$  and  $q$  (both in mg/g) are the amounts of lysozyme adsorbed at equilibrium and at time 't', respectively. The plots of  $\ln(q_e - q)$  versus 't' at different time interval was almost linear, indicating the validity of Lagergren rate equation of first order kinetics. The linear fit between the  $t/q_t$  and contact time (t) for pH can be approximated as pseudosecond order kinetics. The adsorption rate constant ( $K_1$ ), calculated from the slope of the above plot is presented in Table 1. It was observed from the data that the adsorption rate constant values were almost similar for initial lysozyme concentrations of 1, 2, 3 and 4 mg/mL. It was concluded that the adsorption rate constant was independent of initial lysozyme concentration. Also the amount of  $r_1^2$  was more than  $r_2^2$ , it's concluded adsorption of lysozyme on HAP following pseudo first order reaction.

**Effect of temperature**

The effect of temperature on the adsorption of lysozyme with initial concentration 1, 2, 3 and 4 mg/mL onto HAP was studied using optimum contact time (60 min) and the results are presented as percent age removal of lysozyme versus temperature (Fig. 6). The percent age removal of lysozyme with initial concentration 1 mg/mL, increased from 71% to 82%, the percentage removal of lysozyme with initial concentration 2 mg/mL, increased from 74% to 85%, the percentage removal of lysozyme with initial concentration 3 mg/mL, increased from 78% to 88%, and the percentage removal of lysozyme with initial concentration 4 mg/mL, increased from 80% to 91% for 15°C to 45°C temperature.

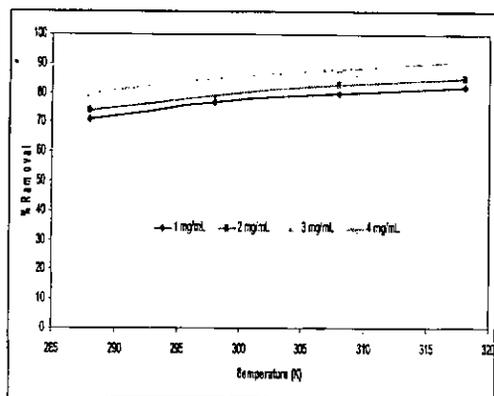

**Fig. 6.** Temperature versus percentage removal of lysozyme with hydroxyapatite, initial lysozyme concentration of 1, 2, 3 and 4 mg/mL (pH=7 and optimum time= 60 min).

It is evident from the figure that, at the temperature of 15 °C the removal was more than 65% and with increase in temperature, the percent age removal increased slowly and reached almost 91%, which indicates the endothermic nature of the process. This was further supported by calculating thermodynamic parameters. The change in free energy ( $\Delta G$ ), enthalpy ( $\Delta H$ ) and entropy ( $\Delta S$ ) of adsorption were calculated using the following equations [28]:


$$\ln K_c = -\Delta H / RT + \Delta S / R \quad (3)$$

$$\Delta G = \Delta H - T\Delta S \quad (4)$$

Where  $\Delta S$  and  $\Delta H$  are the changes in entropy and enthalpy of adsorption, respectively. A plot of  $\ln K_c$  versus  $1/T$  for initial lysozyme concentration of 1, 2, 3 and 4 mg/mL were linear and is represented graphically in Fig. 7. The  $K_c$  value was calculated using the following equation [28].

$$K_c = C_1 / C_2 \quad (5)$$

where  $C_1$  is the amount of lysozyme ion adsorbed per unit mass of HAP and  $C_2$  is the concentration of lysozyme in aqueous solution.

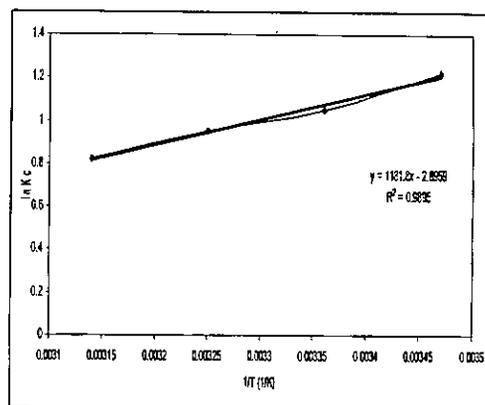

**Fig. 7.** Van't Hoff plots,  $\ln K_c$  versus  $1/T$  for HAP, initial lysozyme concentration of 1, 2, 3 and 4 mg/mL.

Values of  $\Delta H$  and  $\Delta S$  were evaluated from the slope and intercept of Van't Hoff plot sand represented in Table 2. The positive values of  $\Delta S$  indicate some structural changes in the adsorbent and also reflect the affinity of the adsorbent for lysozyme species. The positive value of entropy ( $\Delta S$ ) indicates the increase in randomness so the on going. Negative value of  $\Delta G$  at each temperature indicates the spontaneity of on going adsorption. A decrease in values of  $\Delta G$  with the increase in temperature suggests more spontaneity of lysozyme adsorption at higher temperature. The endothermic nature of the process was once again confirmed by the positive value of enthalpy ( $\Delta H$ ). Positive value of enthalpy ( $\Delta H$ ) suggests that entropy is responsible for making the  $\Delta G$  value negative. So, the adsorption process was spontaneous, since the entropy contribution was much higher than that of enthalpy.

**Table 1.** Rate constants (Pseudo first and second order) obtained from the graph for HAP with different initial concentrations of lysozyme

T(K)	Pseudo first				Pseudo second				
	$q_e^a$	K <sub>1</sub>	$q_e^b$	$k_1^b$	$q_e^a$	K <sub>2</sub>	$q_e^b$	$k_2^b$	
298	2.33	0.05	2.51	0.9871	1.89	0.12	2.12	0.97024	

a: Calculated, b: Experimental

**Table 2.** Thermodynamic parameters using HAP

$\Delta H$ (kJ/mol)	$\Delta S$ (kJ/Kmol)	$\Delta G^{288K}$ (kJ/mol)	$\Delta G^{298K}$ (kJ/mol)	$\Delta G^{308K}$ (kJ/mol)	$\Delta G^{318K}$ (kJ/mol)	R <sup>2</sup>
11.5	0.063	-5.58	-7.12	-7.65	-8.12	0.9895

**Adsorption isotherms**

Analysis of adsorption isotherms are important for developing a model that can be used for adsorption process design and the isotherms obtained under different temperatures can provide basic data for thermodynamics study to deduce adsorption mechanism. In the present work, the results obtained from the equilibrium adsorption experiments, at the temperatures of 288, 298, 308 and 318K and at the lysozyme solution initial pH, were analyzed according to the most frequently employed models Freundlich and Langmuir isotherms [29-31]:

$$Q_e = K_F C_e^{1/n} \tag{6}$$

$$Q_e = \frac{Q_0 K_L C_e}{1 + K_L C_e} \tag{7}$$

And the linear forms of these isotherms are as follows, respectively

$$\ln Q_e = \ln K_F + \frac{1}{n} \ln C_e \tag{8}$$

$$\frac{1}{Q_e} = \frac{1}{Q_0} + \left(\frac{1}{Q_0 K_L}\right) \frac{1}{C_e} \tag{9}$$

where  $C_e$  is the adsorbate equilibrium concentration in the liquid (mg/L);  $Q_e$  is the adsorbate equilibrium amount in solid phases (mg/g);  $Q_0$  is the maximum adsorption capacity according to Langmuir monolayer adsorption (mg/g);  $K_L$  is constant according to the Langmuir isotherm (L/mg);  $K_F$  (mg/g)(L/mg) and  $n$  are Freundlich constants related to adsorption capacity and adsorption intensity of the adsorbent, respectively. The values of  $K_F$  and  $1/n$  can be obtained from the intercept and slope, respectively, of the linear plot of experimental data of  $\ln Q_e$  versus  $\ln C_e$ .  $1/n$  values indicate the type of isotherm to be irreversible ( $1/n = 0$ ), favorable ( $0 < 1/n < 1$ ) and unfavorable ( $1/n > 1$ ) [32]. And the values of  $Q_0$  and  $K_L$  can be calculated from the slope and intercept of the linear plot of  $1/Q_e$  versus  $1/C_e$ . The adsorption

isotherm for lysozyme onto HAP surface is calculated parameters are listed in Table 3.

Based on the correlation coefficient as shown in Table 3, isotherm Langmuir represents a better fit of experimental data than Freundlich and isotherms in all temperature. It indicates that the surfaces of adsorbents are mainly made up of heterogeneous adsorption patches [52] in addition to less homogeneous patches [34]. Freundlich constant,  $n$ , is a measure of adsorption intensity. As seen from Table 3, the values of  $1/n$  for both adsorbents were below 1 at all the experimental temperatures, which indicate high adsorption intensity [35]. The Freundlich constant,  $K_F$ , which is related to the adsorption capacity, also shows that the adsorption capacity increased with temperature increase, indicating that the adsorption processes are exothermic in nature. But the increase of the values of  $1/n$  with the temperature decrease suggests the increasing trend of the adsorption intensity. As temperature increased, the more lysozyme molecules were adsorbed, the keener the competitions for the limited adsorption sites and the stronger the attraction among the molecules, which resulted in increase of adsorption intensity. To compare the adsorption capacity of different surfaces adsorbent towards the lysozyme with that of adsorbents were selected. For lysozyme the adsorption capacity of HAP surface was 38.35 mg/g at 288 K, concentration of lysozyme 1mg/mL and pH 7. The favorability of the lysozyme adsorption process onto adsorbents surfaces evaluated using a dimensionless parameter ( $R_L$ ) derived from the Langmuir expression. It is defined as follows:

$$R_L = \frac{1}{1 + K_L C_0} \tag{10}$$

The adsorption process can be defined as irreversible ( $R_L = 0$ ), favorable ( $0 < R_L < 1$ ), linear ( $R_L = 1$ ) or unfavorable ( $R_L > 1$ ) in terms of  $R_L$  [36].

**Table 3.** Parameters obtained from Langmuir and Freundlich isotherms

HAP Temperature	Langmuir			Freundlich		
	$Q_0$	$K_L$	$R_L^2$	$K_F$	$1/n$	$R_L^2$
288	38.35	1.71	0.942	16.12	0.233	0.912
298	33.12	1.50	0.949	15.88	0.220	0.922
308	30.12	1.32	0.968	15.39	0.212	0.931
318	27.16	1.12	0.968	14.89	0.201	0.940

**Table 4.** The amount of  $R_L$  for adsorption of lysozyme onto HAP

T(K)	Lysozyme concentration (mg/ml)	$R_L$
288	1	0.369
	2	0.226
	3	0.163
	4	0.128
298	1	0.400
	2	0.250
	3	0.182
	4	0.143
308	1	0.431
	2	0.275
	3	0.202
	4	0.159
318	1	0.472
	2	0.309
	3	0.229
	4	0.182

The calculated values of  $R_L$  for adsorption of lysozyme onto HAP fall between 0 and 1, thus the adsorption of lysozyme onto adsorbents is favorable.

## CONCLUSION

HAP was synthesized from egg shell by sole gel method. Synthesis was ascertained by adopting various characterizing methods. HAP exhibited much greater specific surface area. SEM micrograph revealed that the average size of the HAP clusters were 300 nm. Optimum dose of HAP

## REFERENCES

- [1] K. L. Kilpadi, P. L. Chang, S. L. Bellis, Hydroxylapatite binds more serum proteins, purified integrins, and osteoblast precursor cells than titanium or steel. *J Biomed Mater Res* 57(2001)258-67.
- [2] K. Kandori, K., Murata, T. Ishikawa Microcalorimetric study of protein adsorption onto calcium hydroxyapatites. *Langmuir*, 23(2007)2064-70.
- [3] J. M. Gibson, P. Raghunathan, V. Stayton, A solid-state NMR study of the dynamics and interactions of phenylalanine rings in a statherin fragment bound to hydroxyapatite crystals. *J Am Chem Soc* 128(2006) 5364-70.
- [4] G. Yin, Z. Liu, J. Zhan F. X., Ding, N.J. Yuan, Impacts of the surface charge property

was found to be 0.3 g/100mL of synthetic solution. It is evident from the pH study that there was increase in percentage removal for increase in pH from 2 to 6 but for further increase in pH beyond 6, there wasn't any increase in removal. It was found from the study that the equilibrium was established after 40 min. Adsorption of lysozyme was found to follow first order kinetics. The effect of temperature on the adsorption of lysozyme onto HAP was studied using optimum adsorbent dose. It was observed that there was increase in percentage removal of lysozyme with increase in temperature. The effect of initial concentration was studied and was found that the percentage removal of lysozyme decreased from 96% to 80% for initial lysozyme concentration of 100 mg/L to 200 mg/L. The percentage removal was found to remain constant with increase in pH and the optimum pH was found to be 6. The removal of lysozyme by HAP was very efficient and can bring down the lysozyme concentration to its permissible limit. The process can be employed as a primary step for the removal of lysozyme to meet permissible limit of lysozyme in surface and ground water.

## ACKNOWLEDGEMENT

The authors are grateful to acknowledge Islamic Azad University, Islamshahr Branch for financial support.

on protein adsorption on hydroxyapatite. *Chem Eng J* 87(2002) 181-6.

- [5] K. Kandori, M. Mukai, A. Yasukawa, T. Ishikawa, Competitive and cooperative adsorptions of bovine serum albumin and lysozyme to synthetic calcium hydroxyapatite, *Langmuir* 16(2009)2301-5.
- [6] A. A. Sawyer, K.M. Hennessy, S. L., Bellis, Regulation of mesenchymal stem cell attachment and spreading on hydroxyapatite by RGD peptides and adsorbed serum proteins. *Biomaterials* 26(2008)1467-75.
- [7] O. Takagi, N. Kuramoto, M. Ozawa, S. Suzuki, Adsorption/desorption of acidic and basic proteins on needle-like hydroxyapatite filter prepared by slip casting, *Ceram. Int.* 30(2004) 139-143.

- [8] Y. Zhang, Y. Yokogawa, T. Kameyama, Influence of powder particle size of slurries on mechanical properties of porous hydroxyapatite ceramics, *Key Eng. Mater.* 284-286 (2005) 365-368.
- [9] P. Sepulveda, F.S. Ortega, M.D.M. Innocentini, V.C. Pandolfelli, Properties of highly porous hydroxyapatite obtained by the gelcasting of foams, *J. Am. Ceram. Soc.* 83 (2008) 3021-3024.
- [10] D.-M. Liu, Preparation and characterisation of porous hydroxyapatite bioceramic via a slip-casting route, *Ceram. Int.* 24 (1998) 441-446.
- [11] D.M. Liu, Control of pore geometry on influencing the mechanical property of porous hydroxyapatite bioceramic, *J. Mater. Sci. Lett.* 15 (1996) 419-421.
- [12] S. Joschek, B. Nies, R. Krotz, A. Göpferich, Chemical and physicochemical characterization of porous hydroxyapatite ceramics made of natural bone, *J. Biomater.* 21 (2000) 1645-1658.
- [13] Y. X. Pang, X. Bao, Influence of temperature, ripening time and calcination on the morphology and crystallinity of hydroxyapatite nanoparticles, *J. Eur. Ceram. Soc.* 23 (2003) 1697-1704.
- [14] C. Knowles, S. Callcut, G. Georgiou, Characterization of the rheological properties and zeta potential of a range of hydroxyapatite powders, *Biomaterials* 21 (2000) 1387-1392.
- [15] A. Slosarczyk, J.S. Oleksiak, B. Mycek, The kinetics of pentoxifylline release from drug-loaded hydroxyapatite implants, *Biomaterials* 21 (2000) 1215-1221.
- [16] R.M. Schek, E.N. Wilke, S.J. Hollister, P.H. Krebsbach, Combined use of designed scaffolds and adenoviral gene therapy for skeletal tissue engineering, *Biomaterials* 27 (2006) 1160-1166.
- [17] A. Tiselius, S. Hjerten, O. Levin, Protein chromatography on calcium phosphate columns, *Arch. Biochem. Biophys.* 65 (1965) 132-155.
- [18] O. Takagi, N. Kuramoto, M. Ozawa, S. Suzuki, Adsorption/desorption of acidic and basic proteins on needle-like hydroxyapatite filter prepared by slip casting, *Ceram. Int.* 30 (2004) 139-143.
- [19] J.G. Del Rio, P. Sanchez, P.J. Morando, D.S. Cicerone, Retention of Cd, Zn and Co on hydroxyapatite filters, *Chemosphere* 64 (2006) 1015-1020.
- [20] B. Sandrine, N. Ange, B.A. Didier, C. Eric, S. Patrick, Removal of aqueous lead ions by hydroxyapatites: equilibria and kinetic processes, *J. Hazard. Mater.* 139 (2007) 443-446.
- [21] K. Lin, Jiayong Pan, Y. Chen, R. Cheng, X. Xu, Study the adsorption of phenol from aqueous solution on hydroxyapatite nanopowders, *J. Hazardous Materials* 161 (2009) 231-240.
- [22] Prabakaran, K., Kannan, S., Rajeswari, S., 2005. Development and characterization of zirconia and hydroxyapatite composites for orthopaedic applications. *Trends Biomater. Artif. Organs* 18, 114-116.
- [23] Zhai, R.S., Das, A., Hsu, G.K., Han, C.C., Canteenwala, T., Chiang, L. Y., Chuang, T.J., 2004. Polymeric fullerene oxide films produced by decomposition of hexanitro [60] fullerene. *Carbon* 42, 395-403.
- [24] R. Apiratikul, P. Pavasant, Batch and column studies of iosorption of heavy metals by *Caulerpa lentillifera*, *Bioresour. Technol.* 99 (2008) 2766-2777.
- [25] E. Bulut, M. Ozacar, I.A. Sengil, Adsorption of malachite green onto bentonite: equilibrium and kinetic studies and process design, *Micropor. Mesopor. Mater.* 115 (2008) 234-246.
- [26] K.V. Kumar, K. Porkodi, F. Rocha, Comparison of various error functions in predicting the optimum isotherm by linear and non-linear regression analysis for the sorption of basic red 9 by activated carbon, *J. Hazard. Mater.* 150 (2008) 158-165.
- [27] K.Y. Foo, B.H. Hameed, Insights into the modeling of adsorption isotherm systems, *Chemical Engineering J.* 156 (2010) 2-10.
- [28] G. Bayramoglu, M.Y. Arica, Construction a hybrid biosorbent using *Scenedesmus quadricauda* and Ca-alginate for biosorption of Cu(II), Zn(II) and Ni(II): kinetics and equilibrium studies, *Bioresour. Technol.* 100 (2009) 186-193.
- [29] S. Chatterjee, M. W. Lee, S. H. Woo, Adsorption of congo red by chitosan hydrogel beads impregnated with carbon nanotubes, *Bioresource Technology* 101 (2010) 1800-1806.

- [30] Amit Bhatnagar, Mika Sillanpaa, Utilization of agro-industrial and municipal waste materials as potential adsorbents for water treatment—A review, *Chemical Engineering J.* 157 (2010) 277–296.
- [31] Zhenhu Hu, Hui Chen, Feng Ji, Shoujun Yuan, Removal of Congo Red from aqueous solution by cattail root, *J. Hazardous Materials* 173 (2010) 292–29.
- [32] E.R. Alley, *Water Quality Control Handbook*, vol. 8, McGraw Hill, 2000, pp. 125–141.
- [33] Z Aksu, D. Donmez, A comparative study on the biosorption characteristics of some yeasts for Remazol Blue reactive dye, *Chemosphere* 50 (2003) 1075–1083.
- [34] A.S. Ozcan, B. Erdem, A. Ozcan, Adsorption of Acid Blue 193 from aqueous solutions onto BTMA-bentonite, *Colloid Surf. A: Physicochem. Eng. Aspects* 266 (2005) 73–81.
- [35] W.T. Tsai, C.W. Lai, K.J. Hsien, Effect of particle size of activated clay on the adsorption of paraquat from aqueous solution, *J. Colloid Interface Sci.* 263 (2003) 29–34.
- [36] R. Sivaraj, C. Namasivayam, K. Kadirvelu, Orange peel as an adsorbent in the removal of acid violet 17 (acid dye) from aqueous solutions, *Waste Manage.* 21 (2001) 105–110.